



## Hysol® EA 9380

### Out of Autoclave Epoxy Paste Adhesive

Henkel Corporation  
Aerospace Group  
2850 Willow Pass Road  
P.O. Box 312  
Bay Point, CA 94565 USA  
**925.458.8000**  
Fax: 925.458.8030  
www.aerospace.henkel.com

#### Description

Hysol EA 9380 is a low temp curing two-part adhesive that can be applied to large parts via a controlled meter mix operation or via dual cartridge static mixer kits. Hysol EA 9380 offers the strength, toughness and high temp resistance of heat curing film adhesives with greater flexibility and ease of use.

Features	Benefit
Low temp curing two-part adhesive	Low energy cure, long assembly times
Meter mixable	Facilitates automated application or from side by side dual cartridge kits for repair or small volume applications
High strength, toughness and high temp resistance	Film type properties in paste form
Out of Autoclave	Productivity Enhancing

#### Uncured Adhesive Properties

	<u>Part A</u>	<u>Part B</u>	<u>Mixed</u>
Color	Black	White	Grey
Density, mixed g/cc	0.97	0.99	0.974
Viscosity, Poise/Pa.s @ 85°F/30°C (1)	1,800/180	2,150/215	1,600/160
Working Life @ 75°F, hours (2)			3
Surface Carbonation			None
Vertical Slump @ 75°F & 0.12 in thick, in			0.4 inches / 10 mm
Shelf life @ 0°F/-18°C	1 year	1 year	
@ <40°F/4°C	1 year	1 year	
@ 77°F/25°C	4 months	1 year	

Footnotes:

1) Measured using parallel plate rheometry. Measurements made at 10 radians/second.

2) Time available for part assembly with retention of complete adhesive properties, measured in 0.016/0.4 mm thick layer

#### Handling

**Mixing** - This product requires mixing two components together just prior to application to the parts to be bonded. Complete mixing is necessary. The temperature of the separate components prior to mixing is not critical, but should be close to room temperature (77°F/25°C).

<b>Mix Ratio</b>	<b>Part A</b>	<b>Part B</b>
By Weight	100	55
By Volume	100	50

Note: Volume measurement is not recommended for structural applications unless special precautions are taken to assure proper ratios.

### **Application**

**Mixing** - Combine Part A and Part B in the correct ratio and mix thoroughly. Heat build-up during or after cure is normal. Maximum temperature recorded in a 1 lb / 450 g mass was 100°F/38°C.

**Applying** - Bonding surfaces should be clean, dry and properly prepared. For optimum surface preparation consult the Hysol Surface Preparation Guide. Material may pre-heated to 86°F/30°C to improve flow when dispensing from dual cartridge containers.

**Curing** - This adhesive may be cured at temperatures at or above 160°F/70°C. The recommended range is 160°F/70°C to 175°F/80°C for 240 minutes.

**Cleanup** - It is important to remove excess adhesive from the work area and application equipment before it hardens. Acetone and many common industrial solvents are suitable for removing uncured adhesive. Consult your supplier's information pertaining to the safe and proper use of solvents.

### **Bond Strength Performance**

#### **Tensile Shear Strength**

Tensile lap shear strength tested per EN2243-1 after curing 4 hour @ 160°F/70°C. Adherends are 2024-T3 clad aluminum.

<b>Test Temperature, °F/°C</b>	<b>Typical Results</b>	
	<b>psi</b>	<b>MPa</b>
-67/-55	4,650	32
77/25	5,350	37
180/82	4,200	29
250/121	2,500	17

#### **Floating Roller Peel**

Floating roller peel tested per EN2243-2 after curing 4 hours @ 160°F/70°C. Adherends are 2024-T3 clad aluminum.

Floating Roller Peel @ 77°F/25°C, (lb/in) / (N/25 mm) 50 / 220

#### **Compressive Properties**

Compressive Strength @ 77°F/25°C	11,300 psi	78 MPa
Compressive Modulus @ 77°F/25°C	355 ksi	2950 MPa
Shore D Hardness @ 77°F/25°C	77	
Tg dry	200°F	93°C
Tg wet	225°F	108°C

**EA9380 tested with EA9895WPP**

Test	Composite Type	Specimen Conditioning	Test Temperature	EA 9895WPP			
				EA 9696	EA 9380	EA 9360	EA 9360 Sanded
Single Slotted Lap Shear, (SLS), psi  <b>Bonded</b>	Toray F6273C-07M	Dry	-67°F	2851	1281	1241	-
			75°F	2815	1751	1489	3462
			160°F	2998	1432	837	-
		30 days at 158°F / 85% RH	160°F	3309	3207	2827	-
Double Cantilever Beam (DCB), lb/in  <b>Bonded</b>	Toray F6273C-07M	Dry	75°F	6.47	0.78	0.81	1.54

**Service Temperature**

Service temperature is defined as being the onset of the glass transition using a 4 hour @ 160°F/70°C cure. The service temperature is 200°F/93°C.

**Henkel QC Acceptance Testing**

This data sheet provides users with typical properties obtained from this adhesive. These values are not meant to be used to develop aerospace QC acceptance testing. Users interested in establishing values and tests for routine QC acceptance should request the Henkel Aerospace Specification, which provides detail test methods and values used to certify this adhesive.


**Bulk Resin Properties**

Cure, hrs	4 @ 160°F/70°C
Degree of Cure, %	80-85
Tg, onset, as cured	200°F/93°C
Saturated @ 160°F/70°C & 85% RH	225°F/108°C
% H <sub>2</sub> O Absorbed, w/w	4.0

**Film Comparisons**

	Hysol EA 9380 Initial	Hysol EA 9628 1 hour post cure @ 250°F	Hysol EA 9696
Form	Paste	Supported Film	Supported Film
Film Weight, psf	--	0.06	0.06
Support Fabric	None	Non-woven	Non-woven
Cure, hrs	4 @ 160°F/70°C	1.5 @ 235°F/113°C	1 @ 250°F/120°C
Adherends	2024-T3 Clad, Phosphoric Acid Anodize, BR127 Primed	2024-T3 Bare, Phosphoric Acid Anodize, BR127 Primed	2024-T3 Bare, Phosphoric Acid Anodize, BR127 Primed
Tensile Shear, psi/MPa, as cured -67°F/-55°C 77°F/25°C 180°F/82°C 250°F/120°C	4,650 / 32 5,350 / 37 4,200 / 29 2,500 / 17	5,500 / 37.9 5,800 / 40.0 5,100 / 35.2 2,100 / 14.5	6,700 / 46.2 6,300 / 43.5 4,550 / 31.8 2,200 / 15.2
Environmentals, Shear @ 180°F/82°C, psi / 2,000 hr 160°F/70°C @ 85% RH	3,900 / 26.9	2,650 / 18.3	2,750 / 19.0
Bell Peel, (lb/in) / (N/25mm) @ 75°F/25°C	50 / 220	55 / 240	80 / 350
T <sub>g</sub> , As Cured Water Saturated, 160°F/70°C @ 85% RH	210°F/99°C 220°F/104°C	230°F/110°C 180°F/82°C	225°F/107°C 200°F/93°C

### EA9380 - Post Cure Impact

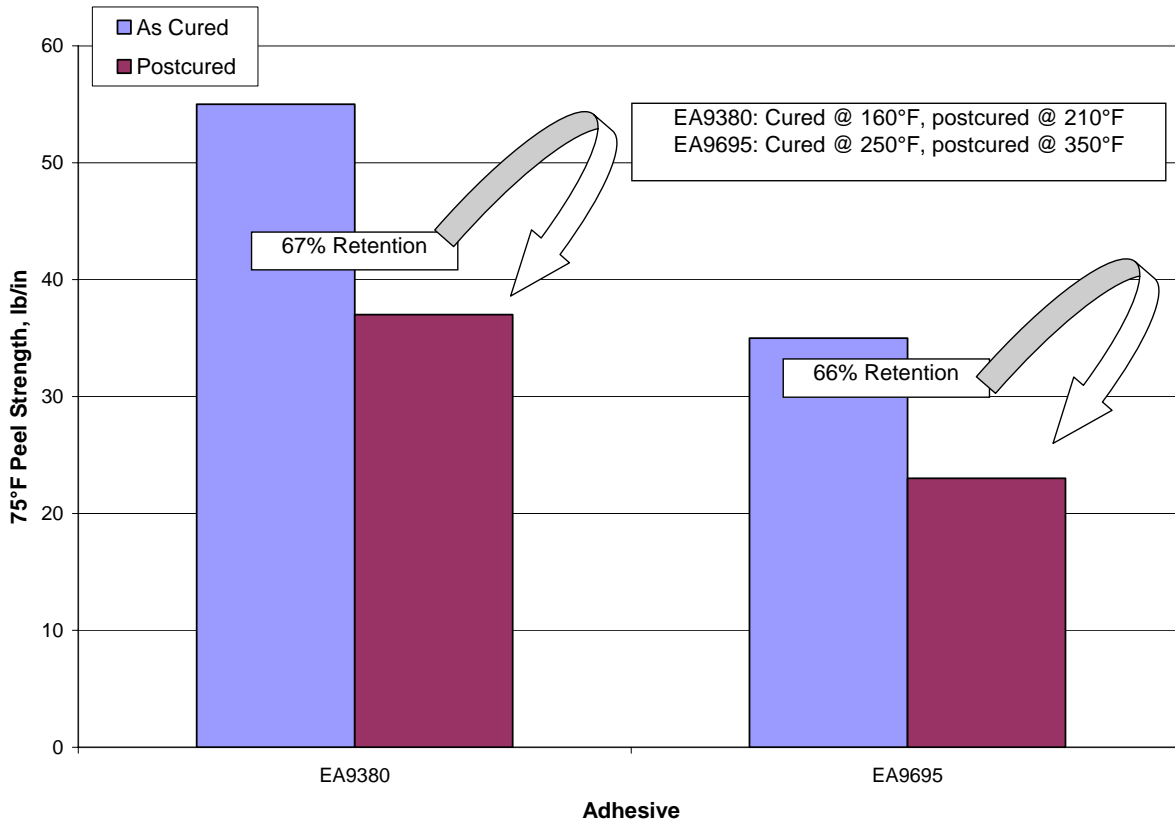

### Handling Precautions

Do not handle or use until the Material Safety Data Sheet has been read and understood.  
For industrial use only.

#### General:

As with most epoxy based systems, use this product with adequate ventilation. Do not get in eyes or on skin. Avoid breathing the vapors. Wash thoroughly with soap and water after handling. Empty containers retain product residue and vapors, so obey all precautions when handling empty containers.

#### PART A

**CAUTION!** This material may cause eye and skin irritation or allergic dermatitis. It contains epoxy resins.

#### PART B

**WARNING!** This material causes eye and skin irritation or allergic dermatitis. It contains amines.

Hysol® is a registered trademark of Henkel Corporation.

Rev. 3/14/2008